

## The History of Deep Mixing in New Orleans

Dr. Donald A. Bruce<sup>1</sup>

Dr. Peter R. Cali<sup>2</sup>

Mark L. Woodward<sup>3</sup>

<sup>1</sup> President, Geosystems, L.P., P.O. Box 237, Venetia, PA 15367, U.S.A., Phone: 724-942-0570, Fax: 724-942-1911, [dabruce@geosystemsbruce.com](mailto:dabruce@geosystemsbruce.com)

<sup>2</sup> President, Sea Level Engineering, LLC, 4912 Lake Vista Drive, Metairie, LA 70006, U.S.A., Phone: 504-862-1001, [prcali@cox.net](mailto:prcali@cox.net)

<sup>3</sup> Geotechnical Engineer, U.S. Army Corps of Engineers, P.O. Box 60267, New Orleans, LA 70160-0267, U.S.A., Phone: 504-862-1006, Fax: 504-862-1091, [Mark.L.Woodward@usace.army.mil](mailto:Mark.L.Woodward@usace.army.mil)

**ABSTRACT:** Although the Deep Mixing Method (DMM) had been conducted in the United States since 1986, it was not until the mighty efforts required to quickly and reliably rebuild the levee system in the aftermath of Hurricanes Katrina and Rita that it was used in the New Orleans area. Whereas the soils had long been judged to be amenable to DMM, other traditional methods of ground engineering had previously been used.

With what with hindsight we can see to have been a singularly astute – or lucky! – decision, the U.S. Army Corps of Engineers, New Orleans District (USACE) commissioned a full-scale DMM field test in typical New Orleans conditions at the beginning of the decade. Though the test was very successful in all regards, the concept of using DMM in routine construction projects was shelved since it was perceived to not be cost effective. However, the technical and scheduling challenges of the Task Force Guardian projects in 2006 overcame this perception and, from that time onwards, there has been a virtually continuous succession of DMM projects, using both Wet and Dry Methods. This path has culminated in the huge project at Lake Ponchartrain, LPV111, discussed elsewhere in this conference.

## INTRODUCTION

It always seemed that the soils underlying New Orleans, LA, and all its flood protection levees and related structures, would be amenable to the benefits of the Deep Mixing Methods (DMM) should the need arise to improve them. In many ways, these soils mirrored, in their properties, those in the birth places of DMM, namely the Nordic Countries and Japan (FHWA, 2000). For example, they comprised similar sequences of soft cohesive sediments of very high moisture contents, and typically high organic contents, often concentrated into specific horizons, of variable lateral and vertical continuity, reflecting their depositional history. However, there must be a problem before there is a solution. Prior to the catastrophic events of late August, 2005, there was no clear and present necessity to introduce a new, exotic technology (i.e., DMM) into a region where foundation solutions were either provided by “traditional” methods (e.g., driven piles) or were simply not required (i.e., the levees were intact).

By an act of greatest good fortune, the authors had met in the mid-1990’s at a geotechnical seminar in New Orleans: the subject of the interface was Deep Mixing, as practiced elsewhere in the U.S., Japan and the Nordic Countries. By the late 1990’s, the New Orleans District, U.S. Army Corps of Engineers, had raised research funding to conduct desk and bench studies of the potential for Deep Mixing in New Orleans conditions, and this lead

logically to the design and implementation of a full-scale test program in representative conditions in 2003.

The results of this test were extremely valuable and informative, not least of all because of the insight it generated regarding the challenges posed by the local soil conditions to efficient, homogeneous mixing. Nevertheless, the absence of a pressing need, allied to the perception that DMM was somewhat too expensive and somehow too sophisticated for local practices, led to the shelving of DMM as a viable and reliable foundation stabilization technology.

By macabre coincidence, the definitive papers on the Test Program were presented at the international DMM conference in Stockholm, Sweden in April of 2005 (Cali et al., 2005a and b), and attracted technical and commercial attention internationally, but also in the U.S. engineering community. In August of that same year, Hurricanes Katrina and Rita devastated the Mississippi Delta region, causing unfathomable human, economic and emotional damage.

USACE established Task Force Guardian, whose mission was to restore the flood protection afforded by the levee and flood wall systems to pre-Katrina levels by June 1, 2006. This involved about 169 miles of repair work. As a direct consequence of the specific goals of the mission, DMM surfaced as a viable construction technique, offering significant technical and scheduling advantages. DMM techniques were therefore used in several emergency projects, and in many medium-sized projects between then (2006) and 2010. This may be regarded as Phase 2 of Deep Mixing in New Orleans.

Thereafter, there has been a third phase, epitomized by the huge LPV 111 project, the subject of several companion papers in this Conference. The deep mixing conducted in that project represents the largest DMM project ever conducted outside of Japan.

The following sections detail the results obtained from the eleven DMM projects conducted in New Orleans and its vicinity, between the original field test program of 2003 and the beginning of the LPV 111 work in 2010. Information is provided on the laboratory (i.e., bench scale) testing and the results of in-situ testing.


## **PHASE 1: THE FULL-SCALE FIELD TEST OF 2001 (Cali et al., 2005a; Cali et al., 2005b)**

With a view to the possible construction of a flood control structure at the Inner Harbor Navigation Channel (IHNC) in New Orleans, a DMM test program was funded by USACE. To satisfy design requirements, the shear strength of the upper 26 feet of native soil had to be increased from the original 350 psf to 2,000 psf. Calculations showed that this could be accomplished with columns of average shear strength 6,060 psf at a replacement ratio of 30%. A test section was a prerequisite since this type of construction had not been used by the USACE before — anywhere.


The goals of the test section were :

- optimize design (and cost estimating) procedures;
- demonstrate the ability of DMM to satisfy the design intent;
- obtain better understanding of column-soil interaction in a slope stability application; and
- establish QA/QC procedures.

The area comprised fill and recent Holocene soils consisting of swamp/marsh deposits, deltaic plain deposits, beach ridge sand deposits, and near shore Gulf deposits to depths equivalent to EL -65 feet. Test details are provided in Figure 1 and are summarized in Figure 2. These conditions are not atypical of the New Orleans areas.

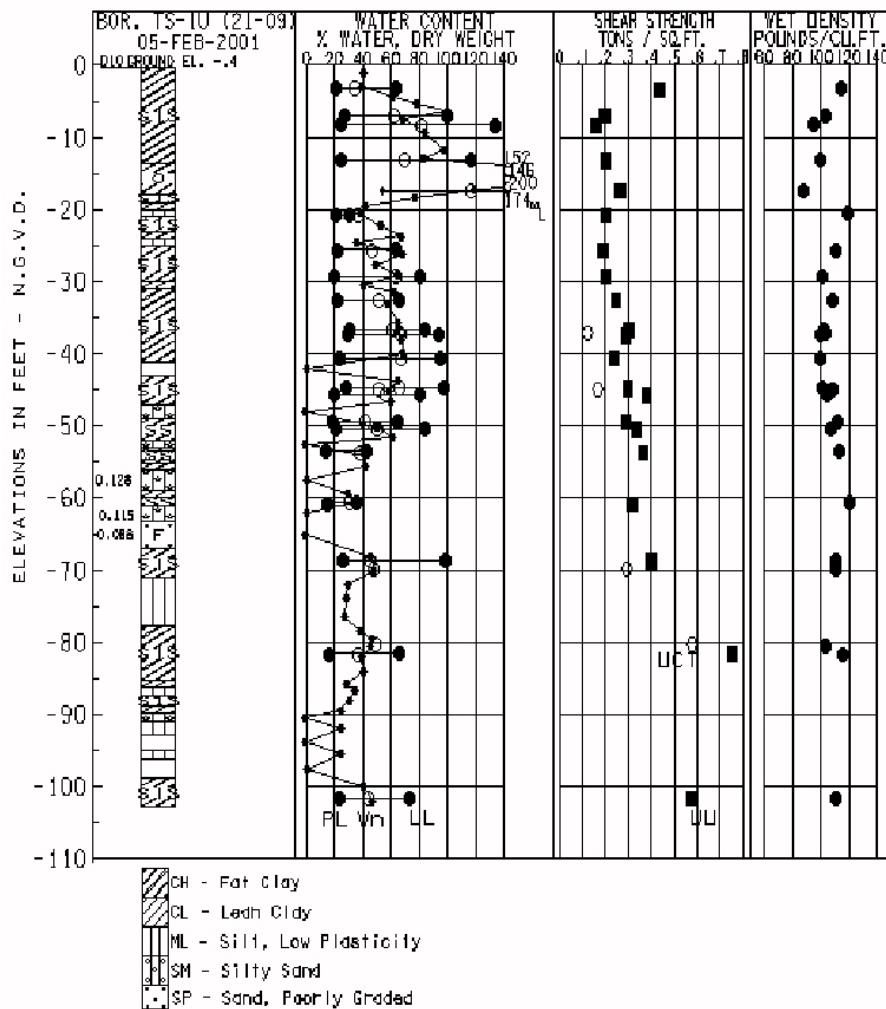

**FIG. 1. Soil properties from one 5-inch diameter, undisturbed boring.**

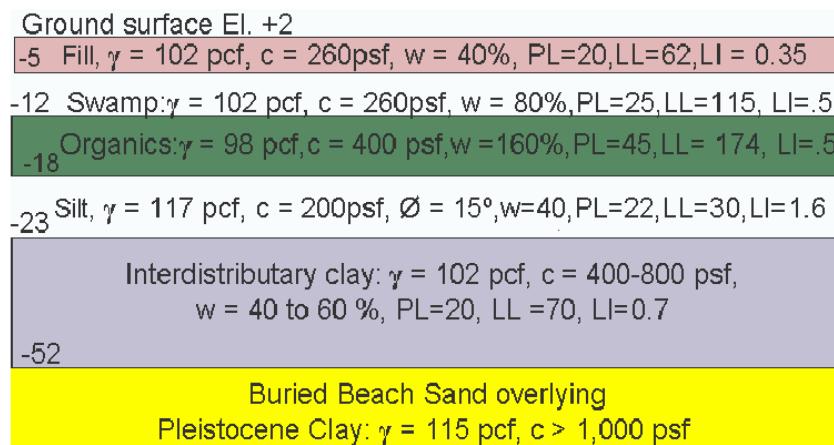

**FIG. 2. Generalized site stratigraphy and soil properties.**

The test program was planned for three phases: a bench scale test and a full-scale test section in two phases, the specific objectives of which were:

- 1) Bench Scale Test and Phase 1 Test – To obtain comparative data regarding the in-situ relationship between column shear strength and column design parameters, such as design mix, loading rate and mixing energy.

- 2) Bench Scale Test and Phase 1 Test – From full-scale column data, adjust the initial design for the Phase II test section so that loading to failure could be achieved.
- 3) Phase II Load Test – To verify column/soil interaction assumptions made for infinite levee slope stability analyses upon which the actual flood protection levee design would be based.
- 4) Phases I and II Test – To study the construction methods, quality test methods, and intangible aspects of construction using lime cement columns.

To accomplish the stated goals, a full-scale test section was loaded to failure in Phase II.

The bench scale test (a dry DMM method was anticipated) featured four different soil types and five different mixtures and dosages of binders, and led to the use of mainly cement, but also lime-cement-columns in the 35-foot-long, 32-inch diameter test columns themselves (Table 1). In addition to the suite of tests shown in this table, the upper 16 feet of four of these columns were excavated (Photograph 1), sealed, inspected, tested in mass, and further cored, to determine the properties obtained, e.g., Figure 3. Many Phase I lessons were learned, not all positive or encouraging given the “learning curve” difficulties of the mixing process, and the variability of the native materials.

**Table 1. As-Built Phase I Columns and Testing**

	MIX COMPOSITION	CEMENT FACTOR (kg/m <sup>3</sup> )	MIX METHOD	TESTING TYPE
1	100% C	150	1	RCPT
2	100% C	150	1	PM
3	100% C	150	1	EXP
4	100% C	150	1	RCPT
5	25% L / 75% C	150	1	PM
6	100% C	134	1	RCPT
7	100% C	200	1	RCPT
8	100% C	130	1	PM
9	100% C	200	1	EXP
10	100% C	139	1	PM
11	25% L / 75% C	200	1	PM
12	100% C	136	1	RCPT
13	100% C	200	1	RCPT
14	100% C	130	2	PM
15	100% C	150	1	EXP
16	100% C	144	1	PM
17	25% L / 75% C	150	2	PM
18	100% C	153	1	RCPT
19	100% C	200	1	RCPT
20	100% C	200	2	PM
21	100% C	200	1	EXP
22	100% C	154	1	PM
23	25% L / 75% C	200	2	PM
24	100% C	150	1	CPT

RCPT = Reverse Column Penetration Test

PM = Pressuremeter

EXP = Exposed for 6' Coring and UU Testing


Columns 2, 5, 8, 11, 14, 17, 20 and 23 were also bored using 3" sampler and UU testing

Mix Method 1 – Injection of binder during both penetration and withdrawal

Mix Method 2 – Same as Mix Method 1 with a remix in Organic layer




**Photograph 1.** Excavated test column.

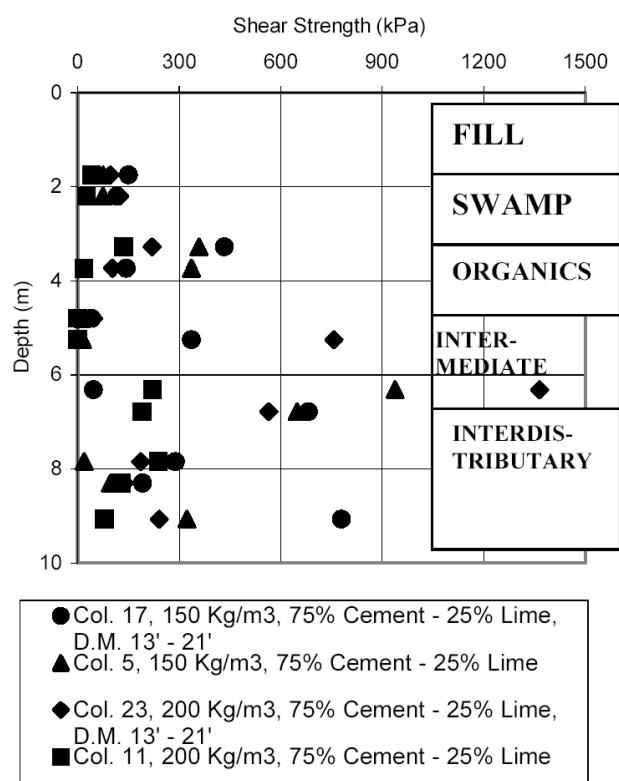

**FIG. 3.** Shear test results on core samples.

Two “test cells,” with 12% and 20% replacement ratios, respectively, were built (Figure 4) with the overlapping columns arranged in panels. All columns were installed with 100% cement binder. Each cell was instrumented to measure load distribution between the soil and columns, pore pressure increase in the soil, and depth and inclination of the failure surface, in real time. An untreated reference cell was also loaded to failure (using the same steel ingots — [Photograph 2](#)) as a baseline condition.

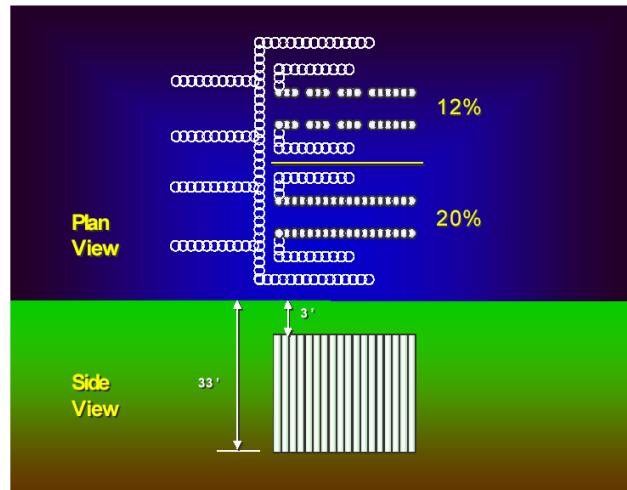

**FIG. 4. As-built cell configuration with 12% and 20% replacement ratios.**



**Photograph 2. Cell A fully loaded with 1 million kilograms of steel (177 kN/m<sup>2</sup>).**

Invaluable information was obtained during this program. In short, while the applicability of (dry) Deep Mixing had been clearly demonstrated, there were sufficient doubts (and, arguably, misunderstandings) about its technical capabilities and its comparative cost effectiveness that it was decided to keep the technique “on ice.”

## PHASE 2: SUMMARY OF PROJECTS 2006-2010

The “ice,” in the form of Hurricanes Katrina and Rita, melted in late 2005 and 2006. As noted above, the requirements placed on Task Force Guardian were such that time was far more of the essence than money, while technical doubts could be compensated by conservatism in design. From early 2006 to mid-2009, there were numerous small- to medium-sized DMM projects which had now attracted the wet methods (Ratio, Inc.) as well as the dry methods, as practiced by Hayward Baker, Inc.

In the majority of projects, the beautiful path was followed in exemplary fashion: bench scale testing, followed by a full-scale field, demonstration test, in turn followed by a closely instrumented and monitored production phase, with later verification of in-situ DMM properties, typically by coring.

Table 2 summarizes these projects — as known to the authors — conducted during this interregnum. Each of these projects generated site-specific data on the relationships between the existing soils, the contractors’ means, methods and materials, and the resultant treated soil properties. All were conducted for the New Orleans District, USACE, which therefore, in its internal resources, and in the offices of its specialty consultants and advisors, developed an extremely pertinent and potent database of experience regarding the use of DMM in the New Orleans area. Of course, not all the experience was good, but it is fair to say that all experiences were instructive.

**Table 2. Summary details of Deep Mixing Projects Conducted  
(all for USCE) in New Orleans, 2006-2010.**

PROJECT NAME	START DATE	APPLICATION	DETAILS	CONTRACTOR
17 <sup>th</sup> Street Canal	2006	Overwater mixing for interim canal closure structure in cellular grid pattern.	2,200 DRE columns, 800 mm diameter, 18 m deep	Hayward Baker, Inc.
Orleans Avenue Canal	2006	Overwater mixing for interim canal closure in rows and “hammer heads.”	Triple axis WRE in rows and square grid. About 6,000 cubic meters of treated soils.	Raito, Inc.
Gainard Woods Pump Station	2006	Emergency levee repair.	Triple axis WRE.	Raito, Inc.
P24 Plaquemines Parish	2006	Foundation stabilization with rows of columns for levee raising.	4,600 DRE columns, 800 mm diameter, 13 m deep	Hayward Baker, Inc.
Westwego Interim Phase 1	2008	Flood wall replacement.	Triple axis WRE.	Raito, Inc.
Westminster Pump Station	2008	Ground improvement for new structure in cellular grid.	DRE columns, 800 mm diameter	Hayward Baker, Inc.
Westwego Pump Station Phase 2	2009	T-wall foundation stabilization.	Triple axis WRE	Raito, Inc.
IHNC Reach III (paper in this Conference)	2010	Soil improvement under I-wall levee section in panels.	DRE columns, 800 mm diameter 11.6 m deep	Hayward Baker, Inc.
LPV-109.02	2010	Levee raising.	Triple axis WRE	Raito, Inc.
WBV-09a	2010	First levee enlargement and pump station	Triple axis WRE	Raito, Inc.

During the period of 2006-2010, the New Orleans area experienced the highest intensity of deep mixing projects in North America, with the possible exception of California, and the Port of Oakland in particular, and all technical — and commercial — eyes in the deep mixing community in the U.S. were firmly focused on New Orleans. This focus was sharpened further by the decision of the USACE to organize “industry days” to brief potential participants about the nature, scale and timing of the anticipated upcoming works. These “works in planning” were of a scale and intensity not heretofore seen in North America and — amongst other natural reactions — attracted growing international interest.

## PHASE 2 – ILLUSTRATIVE DETAILS

At the time of writing, bench scale test data were available for 7 of the 10 New Orleans projects of Phase 2. These are summarized in [Table 3](#).

Regarding the “wet” method adopted by Raito, Inc., their bench scale testing of the Westwego Pump Station soils is typical. They anticipated the use of two cement factors, correlated to column depth (to EL 24 m), and the two predominant soils “organic clay” over “clay.” The test data are summarized in [Table 4](#). For the upper 8 m of organic soils, the experimental data of [Figure 5](#) were obtained. Predictably, the soils of the lower 8-24 m showed significantly higher strengths at all cement factors ([Figure 6](#)).

For the “dry” method, as practiced by Hayward Baker, Inc., the program conducted for the Plaquemines Parish (P24) project is typical. The average soil shear strength of 15 KPa had to be increased to an average of 110 KPa in the composite treated soil mass. This required a column shear strength of 340 KPa (i.e., UCS = 680 KPa) given the typical 30% area replacement ratio. The scope of the test program is summarized in [Table 5](#), while the results are shown in [Figure 7](#).

In-situ testing for Quality Assurance and Verification has been conducted on all 10 of these projects. As for the results of the bench scale testing, two illustrative groups of data are presented.

The “wet” method was used for foundation improvement under the interim closure structure at the Orleans Avenue Canal to a minimum UCS of 830 KPa. The layout of the 0.9 m diameter columns is shown in [Figure 8](#), and the operation is illustrated in [Photograph 3](#). Three percent of the production columns, or four columns per side, were to be tested by wet grab sampling and coring. Results from the wet grab sampling of the critical upper 3 m of organic soils are shown in [Figure 9](#). (350 kg/m<sup>3</sup> cement factor and WCR = 0.8 to assure strength in the very tight schedule restraints). Typical coring based results are shown in [Figure 10](#).

The most detailed information on the “dry” method columns of Hayward Baker, Inc. are those from the 17<sup>th</sup> Avenue interim closure structure project. Prior to production, 12 test columns were installed:

- 4 with a cement factor of 200 kg/m<sup>3</sup> with single treatment of the upper organic layer;
- 4 with a cement factor of 200 kg/m<sup>3</sup> with double treatment of the upper organic layer;
- 4 with a cement factor of 175 kg/m<sup>3</sup> with double treatment of the upper organic layer.

The binder consisted of 75% slag and 25% cement. Columns were cored at 16, 18 and 20 days after installation, providing 32 samples for UCS testing. Results are provided at 28 days in [Figure 11](#). About 15,600 cubic meters of soil was treated on the protected side of the structure, and a further 14,000 cubic meters on the flood side.

**Table 3. Summary of conclusions from bench scale testing of mixed soils, New Orleans.**

Project	Wet/Dry Method	Required Strength <sup>1</sup>	Key Results from Laboratory Mixing Tests <sup>2</sup>
17 <sup>th</sup> Ave	Dry	120 psi	<ul style="list-style-type: none"> <li>Test results are reported for three soil types treated with 75% slag – 25% cement and/or 100% cement, with binder factors ranging from 150 to 400 kg/m<sup>3</sup>.</li> <li>For an organic layer, 75% slag – 25% cement with binder factors of 175, 350, and 400 kg/m<sup>3</sup> produced strengths of about 32, 120, and 230 psi, respectively.</li> <li>For an "intermediate" clay, 75% slag – 25% cement with binder factors of 150, 175, and 200 kg/m<sup>3</sup> produced strengths of 37, 96, and 87 psi. A 100% cement mixture with a binder factor of 175 kg/m<sup>3</sup> produced a strength of 164 psi.</li> <li>For a "bottom layer" soil, 75% slag – 25% cement with binder factors of 150, 175, and 200 kg/m<sup>3</sup> produced strengths of 186, 177, and 213 psi, and a 100% cement mixture with a binder factor of 175 kg/m<sup>3</sup>, produced strength of 130 psi.</li> </ul>
Orleans Ave	Wet	120 psi	<ul style="list-style-type: none"> <li>Only results for an upper organic layer are reported. The binder was 100% cement. Binder factors of 250, 300, and 350 kg/m<sup>3</sup> produced strengths of about 180, 240, and 320 psi, respectively.</li> </ul>
Gainard Woods	Wet	120 psi	<ul style="list-style-type: none"> <li>The soil at this site was primarily a fat clay. Although not stated, we assume here that treatment was with 100% cement. Water-to-cement (w:c) ratios of the slurry were 0.8 and 1.0, and binder factors ranged from 200 to 400 kg/m<sup>3</sup>. Strength test results are reported at 3, 4, and 8 days. The results at 8 days of curing time are summarized here, and it can reasonably be assumed that the 28 day strengths would be much greater.</li> <li>For w:c equal to 0.8, binder factors of 200, 300, and 400 kg/m<sup>3</sup> produced 8-day strengths of about 63, 93, and 99 psi, respectively. For w:c equal to 1.0, binder factors of 200, 300, and 400 kg/m<sup>3</sup> produced 8-day strengths of about 66, 85, and 72 psi, respectively.</li> </ul>

<b>Project</b>	<b>Wet/Dry Method</b>	<b>Required Strength<sup>1</sup></b>	<b>Key Results from Laboratory Mixing Tests<sup>2</sup></b>
Plaquemines Parish Homeplace Levee	Dry	100 psi	<ul style="list-style-type: none"> <li>Test results are reported for Soils A, B, C, and D, which are described as natural levee, swamp-marsh, interdistributary, and intradelta deposits, respectively. The laboratory tests were all conducted using 75% slag – 25% cement, with binder factors ranging from 150 to 200 kg/m<sup>3</sup>.</li> <li>Soil A was treated with 175 kg/m<sup>3</sup>, which produced a strength of about 190 psi. A second test on Soil A with 10% water added to the soil and then treated with 175 kg/m<sup>3</sup> produced mixture strength of 90 psi.</li> <li>Tests on Soil B with binder factors of 175 and 200 kg/m<sup>3</sup> produced strengths of 80 and 78 psi, respectively.</li> <li>Tests on Soil C with binder factors of 175 and 200 kg/m<sup>3</sup> produced strengths of 136 and 133 psi, respectively.</li> <li>Tests on Soil D with binder factors of 150, 175, and 200 kg/m<sup>3</sup> produced strengths of 64, 175, and 203 psi. Additional tests on Soil D with a binder factor of 175 kg/m<sup>3</sup> were performed that showed a lower strength when reduced mixing energy was applied.</li> </ul>
Westwego	Wet	120 psi	<ul style="list-style-type: none"> <li>The soil at this site was divided into an upper zone from 0 to 25 ft depth, and a lower zone from 25 to 80 ft depth. The soils were treated using 100% cement with water-to-cement (w:c) ratios of the slurry equal to 0.8 and 1.0, and with binder factors from 200 to 400 kg/m<sup>3</sup>.</li> <li>For the upper zone soil with w:c equal to 0.8, binder factors of 200 and 300 kg/m<sup>3</sup> produced strengths of about 100 and 165 psi, respectively. With w:c = 1.0, binder factors of 200, 300, and 400 kg/m<sup>3</sup> produced strengths of about 155, 80, and 185 psi, respectively.</li> <li>For the lower zone soil with w:c equal to 0.8, binder factors of 200 and 300 kg/m<sup>3</sup> produced strengths of about 130 and 115 psi, respectively. With w:c = 1.0, binder factors of 200, 300, and 400 kg/m<sup>3</sup> produced strengths of about 185, 160, and 205 psi, respectively.</li> </ul>

Project	Wet/Dry Method	Required Strength <sup>1</sup>	Key Results from Laboratory Mixing Tests <sup>2</sup>
Westminster	Dry	120 psi	<ul style="list-style-type: none"> <li>Three soil types were tested using 100% cement with binder factors ranging from 175 to 450 kg/m<sup>3</sup>.</li> <li>Soil A is described as sandy lean clay and fine sand. Soil A treated with 175, 225, 270, and 450 kg/m<sup>3</sup> produced strengths of 96, 100, 142, and 158 psi, respectively.</li> <li>Soil C is described as fat clay, soft clay, and humus. Soil C treated with 225, 270, and 450 kg/m<sup>3</sup> produced strengths of 59, 78, and 157 psi.</li> <li>Soil D is described as lean clay and soft clay with silt seams. Soil D treated with 175, 225, and 270 kg/m<sup>3</sup> produced strengths of 81, 136, and 228 psi.</li> </ul>
IHNC RIIIB	Dry	84 psi	<ul style="list-style-type: none"> <li>Four soil types were tested: swamp, organic fat and lean clay, intermediate fat and lean clays, and interdistributary fat and lean clays. Treatment was with 50% cement – 50% quicklime and with 100% cement. Binder factors ranged from 100 to 200 kg/m<sup>3</sup>.</li> <li>Only a binder factor of 200 kg/m<sup>3</sup> produced the required strength for the swamp soil, and none of the binders or binder factors tested produced the required strength for organic clay.</li> <li>For the intermediate clay and the interdistributary clay, the 50-50 cement-quicklime mixtures at 150 kg/m<sup>3</sup> produced higher 56 day strengths than the 100% cement mixtures at 150 kg/m<sup>3</sup>.</li> </ul>


Notes:

<sup>1</sup> The strengths listed are unconfined compression strengths.


<sup>2</sup> The strengths listed are the unconfined compression strengths of the mixtures at 28 days of curing time, unless otherwise noted.

**Table 4. Westwego soil classification and bench mix proportions (Thompson, 2008).**

Sample ID	Soil Type	Binder Loading	Binder Mixing (slag / cement)	Slurry Water-Cement Ratio
WBV 1-1	'organic clay'	200 kg/m <sup>3</sup>	pure cement (0/100)	1.0
WBV 1-2	'organic clay'	300 kg/m <sup>3</sup>	pure cement (0/100)	1.0
WBV 1-3	'organic clay'	400 kg/m <sup>3</sup>	pure cement (0/100)	1.0
WBV 1-4	'organic clay'	200 kg/m <sup>3</sup>	pure cement (0/100)	0.8
WBV 1-5	'organic clay'	300 kg/m <sup>3</sup>	pure cement (0/100)	0.8
WBV 2-1	'clay'	200 kg/m <sup>3</sup>	pure cement (0/100)	1.0
WBV 2-2	'clay'	300 kg/m <sup>3</sup>	pure cement (0/100)	1.0
WBV 2-3	'clay'	400 kg/m <sup>3</sup>	pure cement (0/100)	1.0
WBV 2-4	'clay'	200 kg/m <sup>3</sup>	pure cement (0/100)	0.8
WBV 2-5	'clay'	300 kg/m <sup>3</sup>	pure cement (0/100)	0.8

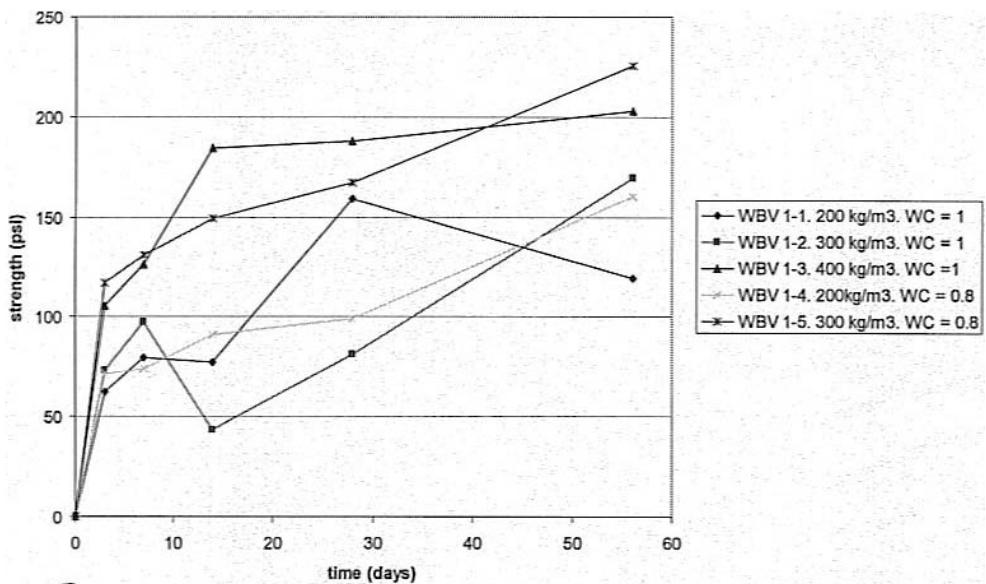


**FIG. 5. Westwego Pump Station, 56-day bench scale results of the upper 25 feet (Woodward, 2008).**

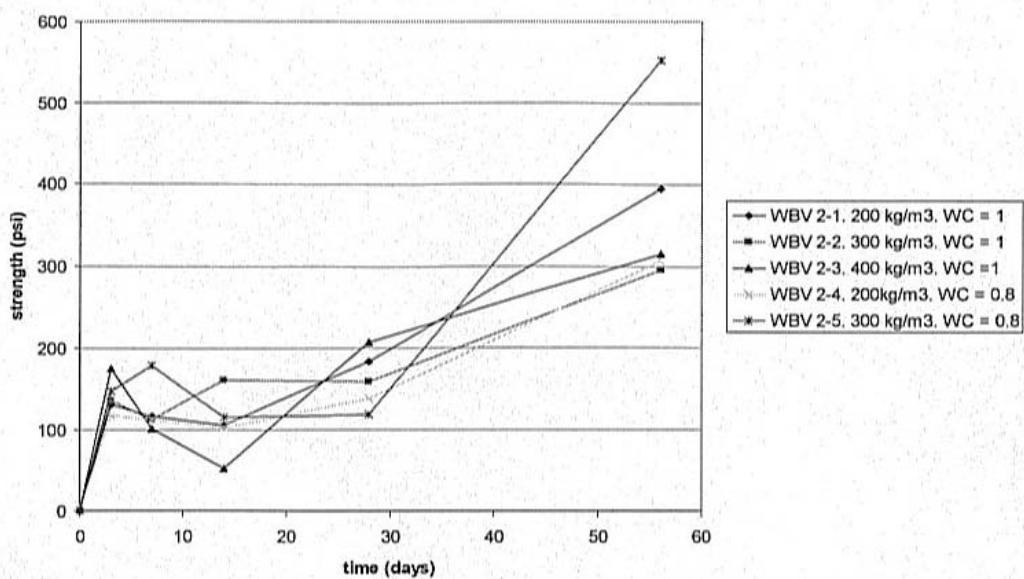


**FIG. 6. Westwego Pump Station, 56-day bench scale results at 28 to 80 feet (Woodward, 2008).**

**Table 5. Plaquemines Parish, Homeplace Levee Setback, soil classification and batch mix designs (Woodward, 2006).**

Soil ID	Approx. Depth (ft)	Soil Type	Binder Loading	Binder Mix (slag / cement)	No. of Samples
A175	0 to 11	'Natural Levee': predominantly fat and lean clays and silts with some sands; low water content	175 kg/m <sup>3</sup>	slag / cement (75/25)	8
A175W			175 kg/m <sup>3</sup>	slag / cement (75/25) + 10% add. moisture	8
B175	11 to 23	'Swamp-Marsh': predominantly organic clays, fat clays and peats with occasional sand and silt layers.	175 kg/m <sup>3</sup>	slag / cement (75/25)	8
B200			200 kg/m <sup>3</sup>	slag / cement (75/25)	8
C175	23 to 35	'Interdistibutary': Interbedded layers of fat and lean clays, silts, silty sands, and sands.	175 kg/m <sup>3</sup>	slag / cement (75/25)	8
C200			200 kg/m <sup>3</sup>	slag / cement (75/25)	8
D150	35 to design depth	'Intradelta': predominantly silt, silty sand and sand.	150 kg/m <sup>3</sup>	slag / cement (75/25)	8
D175			175 kg/m <sup>3</sup>	slag / cement (75/25)	8
D175L			175 kg/m <sup>3</sup>	slag / cement (75/25)	12
D175H			175 kg/m <sup>3</sup>	slag / cement (75/25)	12
D200			200 kg/m <sup>3</sup>	slag / cement (75/25)	8

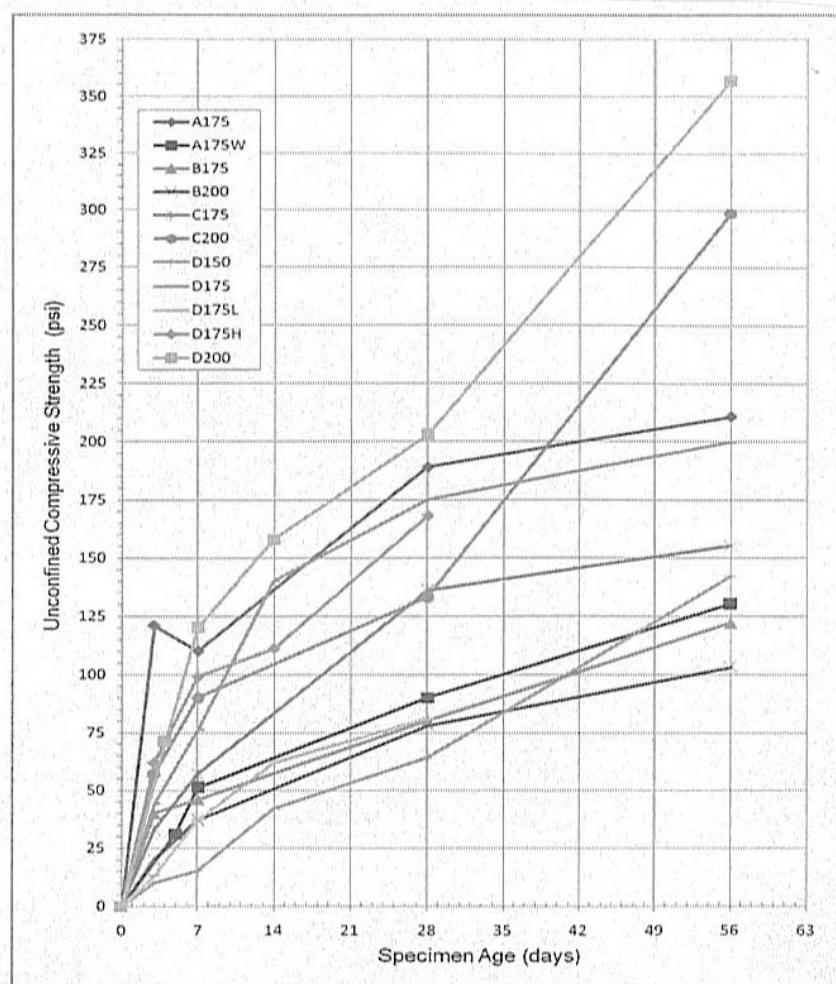


**FIG. 7. Bench scale test results, Plaquemines Parish Homeplace Levee Setback (Woodward, 2006).**

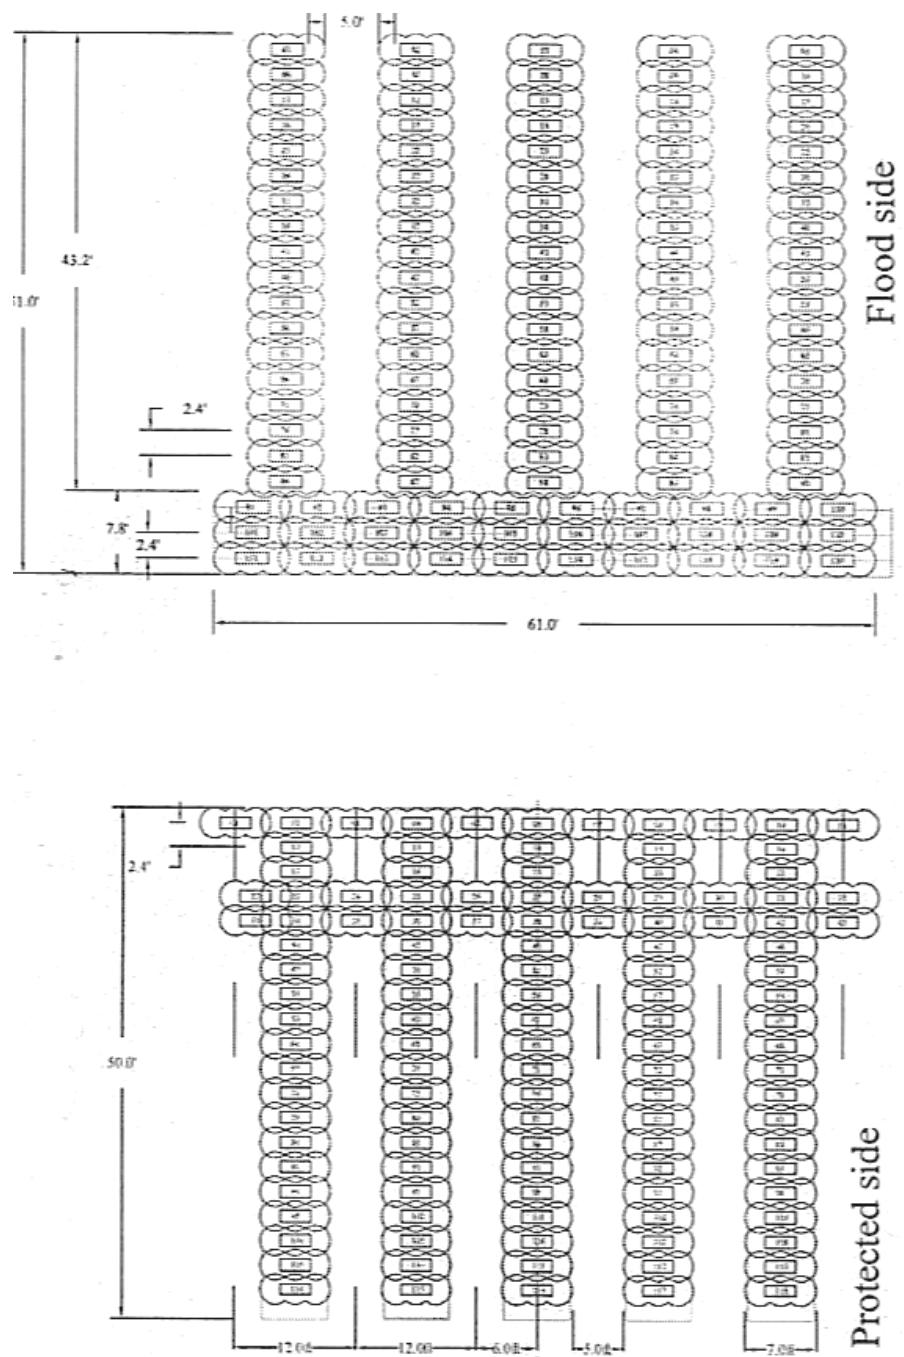


**FIG. 8. Layout of DMM columns, Orleans Avenue Canal, New Orleans (Woodward, 2006).**




**Photograph 3. DMM operations from barge at Orleans Avenue Canal, New Orleans.**

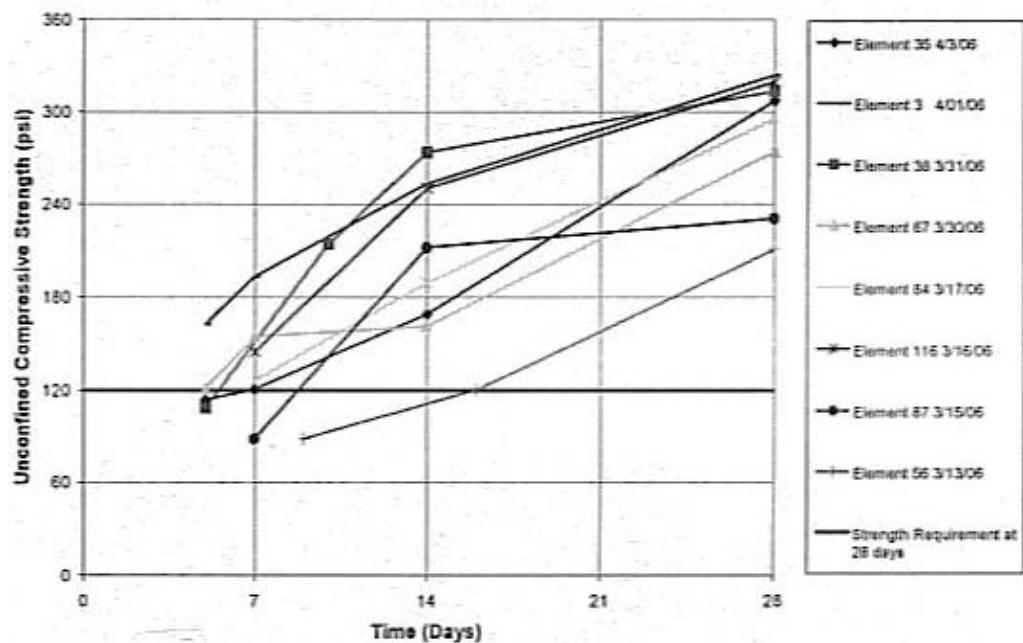

**FIG. 9. Wet grab sample results, upper 10 feet, Orleans Avenue, New Orleans.**

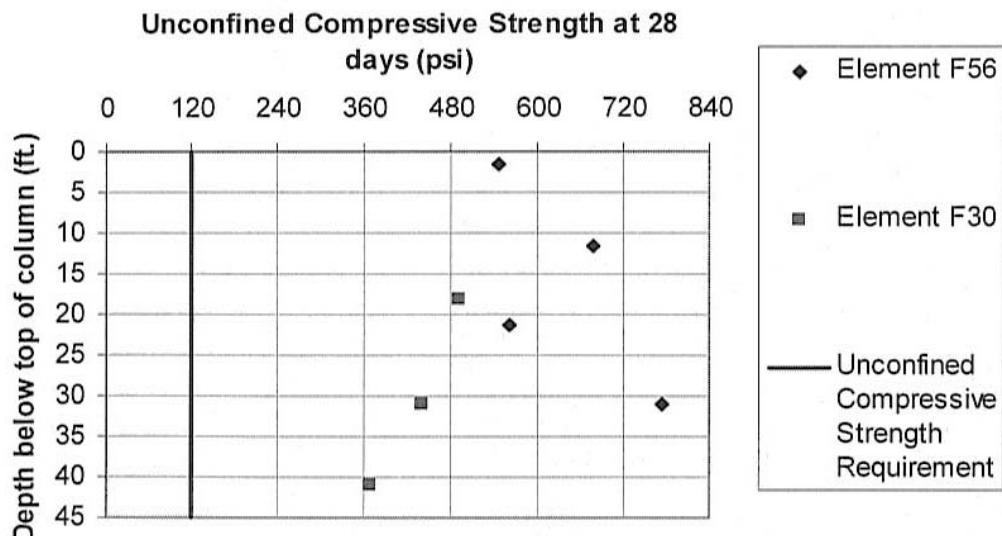

**FIG. 10. Orleans Avenue, in-situ column coring results at 28 days (Woodward, 2006).**

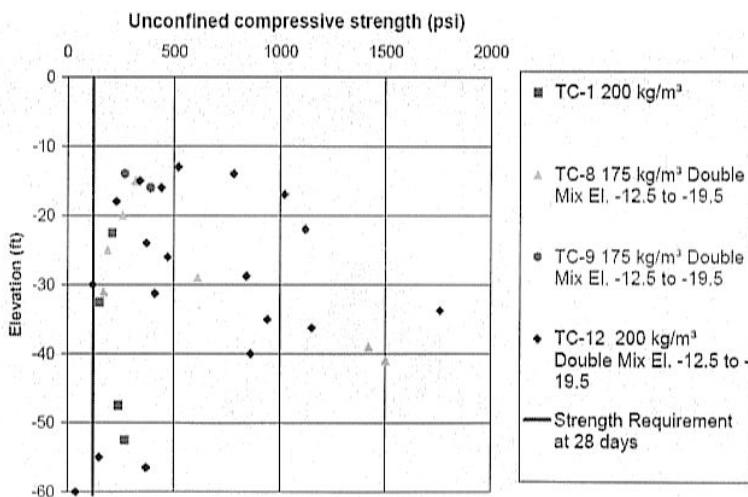


**FIG. 11. Unconfined compressive strength results of in-situ test columns, 17<sup>th</sup> Avenue Canal, New Orleans.**

### PHASE 3: LPV 111

As part of the Lake Pontchartrain and Vicinity Hurricane Protection System, the levee enlargement project identified as LPV-111 presented challenges that required innovative approaches in design, contracting, and construction. LPV-111 extends 9 km along the north bank of the Gulf Intracoastal Waterway (GIWW), bordered on both sides by the Bayou Sauvage National Wildlife refuge. This constricted levee construction to the existing right-of-way, making DMM an effective means for reducing cost and schedule.

Subsurface conditions, fully described in Cooling et al., (2012), consist of clayey levee fill over soft clays, peat, and organic clays to a depth of about 21.3 m below the crest of the existing levee. Underlying the soft clays are stiff Pleistocene age clays

and medium dense sands. Shear strength and wet density profiles are shown in Figure 12.

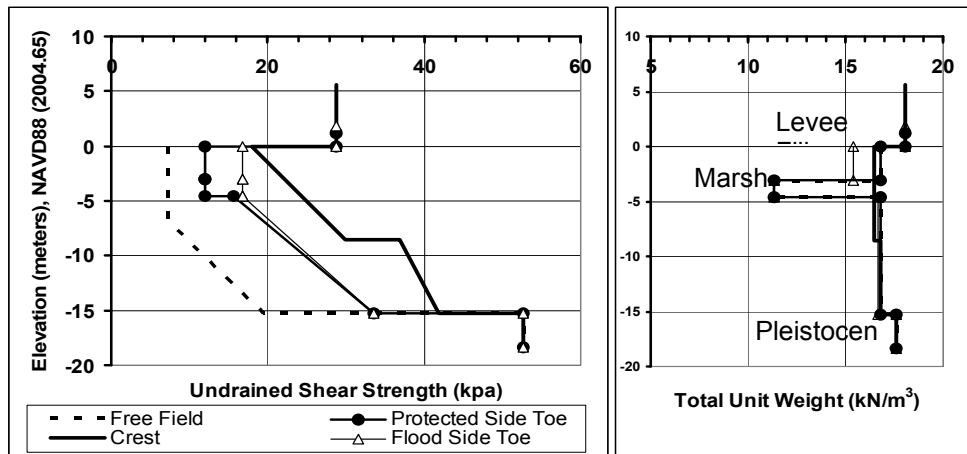


**FIG. 12. Design undrained shear strength and total unit weight, reach 12B (Cooling et al., 2012).**

To enlarge the existing levee by 3.3 m, and meet the more stringent design standards of the Hurricane and Storm Damage Risk Reduction System (HSDRRS), DMM panels were used to buttress the levee against shear failure and to reduce settlement to a negligible level. Overlapping columns were installed 20.3 m through a level working platform and into the foundation, as shown in Figure 13. Excess return material, which was a blend of binder and foundation soil, generally fat clay of medium consistency, was used to construct the levee core. The return material, termed Recycled Embankment material (REM), proved to be highly competent levee fill, having properties similar to the columns. Using REM proved to be an excellent business decision that saved construction time and cost. Design methodology and use of Early Contractor Involvement (ECI) as the acquisition plan for contract award to accelerate construction are described in Cali et al. (2012) and Cooling et al. (2012). ECI allowed design and construction to partner for the betterment of both. The result was project completion on time, within budget, and to the highest industry standards.

As detailed in a companion paper, Bertero et al. (2012), the material used for the project consisted of binder, consisting of 25% type I/II Portland Cement and 75% slag cement, and potable (city) water. For the entire project, over 417,000 tonnes of binder was used. Over 454,000 cubic meters of water was used.

Two different technologies were applied to treat over 1.4 million cubic meters of foundation soil: 1) TREVIA Turbo Mix (TTM), single and double axis and 2) FUDO Contrivance Innovation Cement Mixing Columns (CI-CMC) to create about 18,000 columns having diameters 1.6-m, as detailed in Schmutzler et al. (2012).

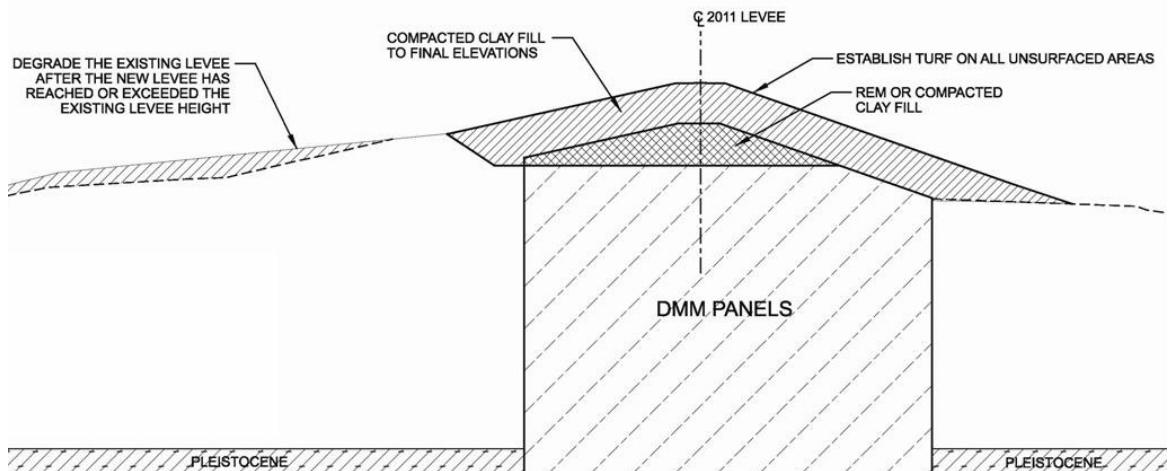

**FIG. 13. Typical LPV 111 Levee Cross Section (Bertero et al., 2012).**

LPV 111 is the largest DMM project ever undertaken in the United States. New ground was broken on several fronts as part of the innovative DMM design, including development of a comprehensive limit equilibrium design methodology, and preparation of meaningful sampling and testing specifications. Advances in mixes and equipment helped optimize cement usage that averaged over 2,000 tonnes per day. Use of REM as part of the levee fill was another first use for flood protection embankments.

Advances made and lessons learned during project design and construction are shared in the accompanying series of five interconnected technical papers in this Conference.

- Overview of Deep Mixing at Levee LPV 111, New Orleans, LA (Cali et al. (2012)
- Deep Mixing Design for Raising Levee Section, LPV 111, New Orleans, LA (Cooling et al. 2012)
- Construction Operations and Quality Control of Deep Mixing at Levee LPV 111 in New Orleans (Schmutzler et al. 2012)
- Bench-Scale testing and Quality Control/Quality Assurance Testing for Deep Mixing at Levee LPV 111 (Bertero et al. 2012)
- Use of Deep Mixing Return Material for Levee Construction at LPV 111 (Druss et al. 2012).

## OVERVIEW

DMM has been used to great advantage in New Orleans for the enlargement of levees and reinforcement of floodwalls in the aftermath of Hurricane Katrina in 2005. In deciding whether DMM is the right solution for levee enlargement, one must consider the elimination of consolidation settlement in the foundation and the savings potential to elimination of future enlargements. In addition, the beneficial use of mixing spoil, which provides a very suitable construction material, should be considered in the economic analysis.

Many levee enlargement projects slated for construction by the USACE for which DMM can be a valuable tool are yet to be designed. Notably, hurricane protection levee enlargements along the Mississippi River in Plaquemines Parish and the 70-miles long Morganza to the Gulf Hurricane Protection Levee, which has to date fallen victim to federal budgetary constraints. The eventual goal of the USACE is to raise the hurricane protection levee and floodwall system to the higher 2057 hydraulic grade, accounting for sea level rise and regional subsidence. For some areas, environmental concerns and right-of-way constraints alone will dictate the use of DMM reinforced levees or conversion of levees to floodwalls.

Only the Morganza to the Gulf project has potential to rival the LPV 111 levee in scale of DMM effort, but still much work remains. Given the current national sentiment in the U.S. to reduce federal spending on all levels, no doubt spending on infrastructure, including flood protection, will suffer. But this will likely result in increased use of ground improvement methods such as DMM that produce overall savings in cost and schedule.

## REFERENCES

- Bertero, A., F.M Leoni, G. Filz, M. Nozu and D. Druss. (2012). “Bench-Scale Testing and Quality Control/Quality Assurance Testing for Deep Mixing at Levee LPV 111,” Fourth International Conference on Grouting and Deep Mixing, Organized by International Conference Organization for Grouting, Managed by Deep Foundations Institute, February 15-18, New Orleans, LA.
- Cali, P., Woodward, M.L., Bruce, D.A., and Forte, E. (2005). “Levee Stability Application for Deep Mixing (1) – Design for Full Scale Test Section Using Dry Mixed Soil Cement Columns”. Deep Mixing 05, Stockholm.
- Cali, P.R. B. Lelong, D.A. Bruce, S. Valagussa, J. Beckerle, J. Gardner, and G. Filz. (2012). “Overview of Deep Mixing at Levee LPV 111, New Orleans, LA,” Fourth International Conference on Grouting and Deep Mixing, Organized by International Conference Organization for Grouting, Managed by Deep Foundations Institute, February 15-18, New Orleans, LA.
- Cooling, T., A. Boeckmann, G. Filz, P. Cali, J. Evans, and F. Leoni. (2012). “Deep Mixing Design for Raising Levee Section, LPV 111, New Orleans, LA,” Fourth International Conference on Grouting and Deep Mixing, Organized by International Conference Organization for Grouting, Managed by Deep Foundations Institute, February 15-18, New Orleans, LA.
- Druss, D., A. Wilding, T. Cooling, J. Beckerle, W. Schmutzler and J. Gardner. (2012). “Use of Deep Mixing Return Material for Levee Construction,” Fourth International Conference on Grouting and Deep Mixing, Organized by International Conference Organization for Grouting, Managed by Deep Foundations Institute, February 15-18, New Orleans, LA.
- Federal Highway Administration. (2000). “An introduction to the deep mixing method as used in geotechnical applications.” Document No.FHWA-RD-99-138, March, 143 p.; “Supplemental reference appendices for an introduction to the deep mixing method as used in geotechnical applications.” Document No. FHWA-RD-99-144, 295 p.; and “An introduction to the deep mixing method as used in geotechnical applications: Verification and properties of treated soil.” Document No.FHWA-RD-99-167, 434 p. Prepared by Geosystems, L.P.

- Schmutzler, W., F.M. Leoni, A. Bertero, F. Leoni, P. Nicholson, D. Druss and J. Beckerle. (2012). Construction Operations and Quality Control of Deep Mixing at Levee LPV 111 in New Orleans,” Fourth International Conference on Grouting and Deep Mixing, Organized by International Conference Organization for Grouting, Managed by Deep Foundations Institute, February 15-18, New Orleans, LA.
- Thompson, J.E. (Email communication, “Mix Design Summary 14-day”. February 19, 2008).
- Woodward M.L., (2008). US Army Corps of Engineers, New Orleans, LA. “Deep Mixing Soil Improvements” Midwest Levee Conference, St. Louis, Missouri.
- Woodward M.L., P.E., US Army Corps of Engineers, New Orleans, LA. (2006). “Three Deep Mixing Applications for Task Force Guardian” Association of State Dam Safety Officials Annual Conference, Boston, Massachusetts.